

**It's Easy!**  
Order all your  
supplies for this  
project on-line or  
at Tech Support:  
**661.823.0108**  
Mon - Fri  
7:30am-4pm PST

## Making a Fiberglass Mold

Fiberglass molds are commonly used to make multiple copies of a part which may have a complex shape. Some of the advantages of using a fiberglass mold are: they are easy to make, the materials are inexpensive, they will last for many years and can be used to produce hundreds of parts. The process starts with a pattern that you wish to copy. In this case I have started with a vacuum formed cowl from a model kit. This is a common part that any modeler may want to copy in fiberglass. The pattern could also be shaped from balsa or foam and finished to achieve a glossy surface.



### Step 1

First you must decide how many parts you will need to divide the mold into, in order to easily lay up the parts. In order to remove the rigid parts from the mold, you must have a positive relief angle on all the mold parts. This means that the mold cross section must get wider as you go from the deepest part of the mold to the outer edges. For these reasons and because this pattern has a seam horizontally dividing the cowl, I decided to make a two part mold dividing the mold along the pattern seam. The parting surface of the mold defines how the multiple parts of the mold will fit together. This surface is created by building up a parting board that divides the cowl shape in half.



### Step 2

The parting board is simple, a few scraps of balsa wood glued together to form a U shaped partition that fits over the cowl. In order to achieve a smooth glossy surface on the mold, a piece of .014 Mylar is contact cemented to the balsa scraps. Similarly the mold surface along the back edge of the cowl is defined with a scrap of foam and a sheet of Mylar. The cowl pattern and the parting surface forms are held in place with Chavant modeling clay on the back of each surface.



### Step 3

Around the edges of the cowl pattern the small openings must be sealed. This can be done with modeling clay by pressing clay into the corners and openings then trimming away the excess material with a model knife or razor blade. In this case, the light weight plastic pattern can be distorted if you press too hard. So be careful that the intended shape is preserved.



**Continue to Step 4...**

## Making a Fiberglass Mold, Cont.

### Step 4

After all the excess clay is removed, the surfaces of the pattern and parting surfaces must have mold release applied. It is important to apply both Partall mold release wax and a liquid mold release. The Partall wax is applied by wiping on a layer waiting a few minutes for the wax to harden then buffing off the surface to a shine. The waxing is then repeated; the number of times will depend on the surface. If you have a glossy completely smooth surface like the Mylar plastic, two or three coats of wax will be enough. However if the surface has any potential for porosity or tiny bubbles in the surface finish, up to ten coats of wax are needed. These layers of wax will fill the tiny surface imperfections. If you have any doubt about the surface, add a couple more layers of wax. The epoxy will lock into these imperfections if you don't use enough wax. Then apply a complete layer of liquid mold releases. I recommend the Safelease products as they can be wiped on with a cloth and dry in about 30 minutes.



### Step 5

Now you are ready to start applying the layers of epoxy and glass cloth. Use the following West System materials:

**105 Resin** is a low viscosity resin that easily wets out the cloth and allows you to minimize air bubbles between cloth layers.

**205 Fast Hardener** allows you sufficient time to wet out each layer, then gels up quickly so that the mold building process can be completed in a few hours.

**406 Colloidal Silica Filler** is used to thicken the epoxy system to aid in applying epoxy to vertical surfaces and filling corners and details in the mold.

**423 Graphite Powder** is used to give the tooling gel coat layer of the mold a black color and a harder surface.




### Step 6

The black color is important when wetting out glass against the mold surface because air bubbles and dry places in the glass are white while the properly wet out glass is transparent showing the black surface. The high contrast makes it easier to produce high quality parts. Mix tooling gel coat from West System 105 Resin with 205 Hardener and about a teaspoon of Graphite Powder. Then stir in a little Colloidal Silica to get a mixture that has the viscosity of ketchup. You need to be able to brush on a thin layer, (.010" to .020") and have a mixture that will stay on the vertical surfaces. Begin by brushing a thin layer in all of the corners. Be careful to not trap any air in the corners as you apply this layer; this is a common problem particularly if you mix the gel coat to thick.



### Step 7

Now apply the gel coat layer over the remainder of the surface. Next mix a little more Colloidal Silica into the resin in the pot to increase the viscosity. Apply some additional gel coat to the corners of the mold to fill in any small radii corners. It is difficult to wet out the glass cloth and keep it in corners of less than 1/4" radius. By filling the corners now you are making the glass application easier.

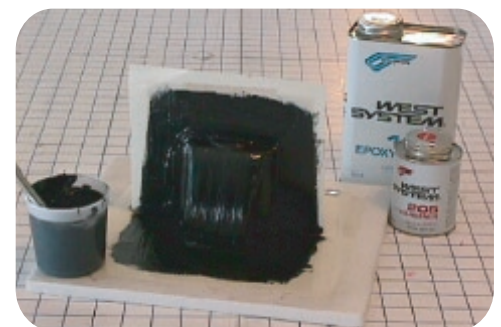


Continue to Step 8...

## Making a Fiberglass Mold, Cont.

### Step 8

Use a coarse weave glass to lay up the mold. I recommend CST style G3733 glass, it is about a yard square. It wets out easily and builds up thickness more quickly than lighter materials.

If the mold has a complex shape like the cowl mold we are building cut the glass on the bias so the fibers run on a diagonal and cut the material into strips 2 to 3 inches wide. This way the cloth will stretch and distort as needed to follow the surface.

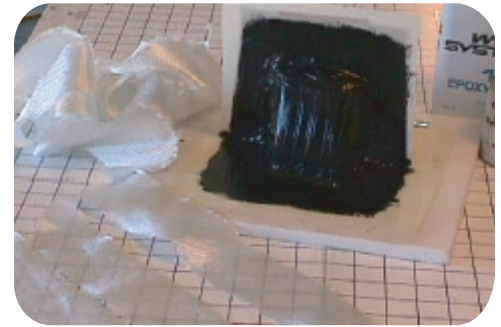

### Step 9


Let the gel coat layer of epoxy set up for about 30 minutes. The epoxy should have set to the point where the surface is only a little tacky. Now mix up another batch of West System Epoxy 105/205 and brush a liberal layer on top of the gel coat layer and begin laying strips of glass on the surface. Whenever possible, apply the epoxy first then lay the dry cloth down. This wets out the glass from the bottom displacing the air in the fabric with less chance of trapping air under the layer of fabric.



### Step 10

Continue wetting out strips of fabric until you have at least two layers of cloth over the entire surface.

Now let this layer set up for about 30 minutes just as you did the gel coat layer. The curing time between layers is not critical. It must be long enough for the epoxy to gel and be only slightly tacky as a minimum and short enough that the epoxy is not nearly cured. So something between 30 minutes and 4 hours will work for a 70 degree shop temperature.

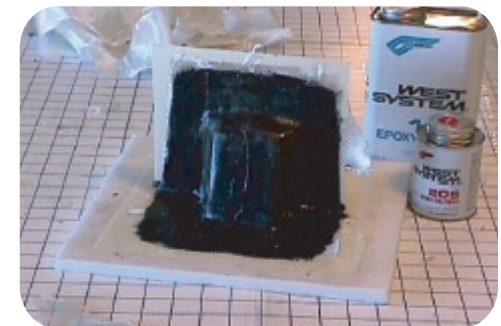

### Step 11

Because the mold will need to be strong and rigid, we need to build up the thickness of the mold. An easy way to do this is to add a layer of Coremat. It is about 1/10 inch thick and can be easily cut to any shape. Cover most of the area with Coremat or a thin chopped strand mat could also be used. Wet this layer well and let the epoxy set up for about 30 minutes then apply another layer of glass cloth as you did previously.



### Step 12

Set the mold aside and let it cure overnight. The next day remove the vertical parting board that the vertical surface of the mold was built against. Clean up any clay that may be left on the pattern.

With a Dremel tool and a 1/4 inch ball cutter, cut four small recesses into the vertical parting surface corners about 1 inch away from the pattern. These will key the second half of the mold into the first half. Now repeat steps 6 through 11 above to build a second half of the mold against the first half. Mold release, gel coat, glass cloth, Coremat, glass cloth and let it cure overnight.




**Continue to Step 13...**

## Step 13

# Making a Fiberglass Mold, Cont.

The next day remove the foam base and Mylar layer from the aft edge of the cowl. Then use a Dremel tool with a reinforced cut off wheel to trim all the rough edges off of the molds. Now carefully separate the mold halves. You may need to use a model knife in one corner to start separating the molds. Twist the knife a little then put a thin strip of wood or plastic in the space and run it around the mold to separate the halves. The mold is now completed and you are ready to start molding fiberglass cowls.

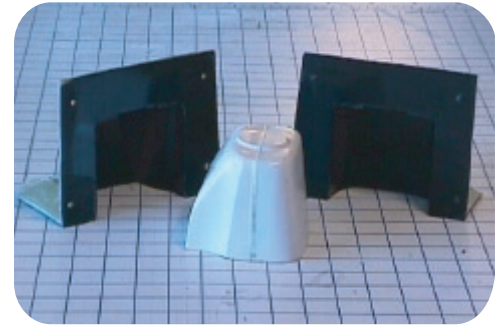

**Click here  
to buy  
these  
products!**

## Supplies to complete this project:

- Molding Supplies: [Mylar 0.014" thick V210 or V211](#)  
[Chavant #307 Professional Modeling Clay M307](#)  
[Safelease 20 Mold Release V203](#)  
[High Temperature Wax V207](#)
- Fillers: [Colloidal Silica A406](#)  
[Graphite Powder A423](#)
- Core Material: [Coremat H2000](#)
- Fiberglass: [5.8 oz. Fiberglass cloth G3733 either 38" or 50" wide](#)  
*(Sometimes referred to as 6 oz. boat & tooling glass)*
- Epoxy: [WEST SYSTEM Resin A105](#)  
[WEST SYSTEM Hardener A205](#)  
*(If you prefer a longer working time, refer to the [WEST SYSTEM Epoxy Selection Chart](#), as A206 or A209 will also work.)*  
[Metering Pumps A300](#)
- Epoxy App. Tools: [Reusable Mixing Sticks A804-8](#)  
[Reusable Mixing Pots A5001](#)  
[Disposable Glue Brushes A803-12](#)  
[Disposable Gloves A832-4](#)

*We also offer two different kits that contain everything EXCEPT the epoxy, which needs to be ordered separately.*

- Kits: [Deluxe Molding Kit for large or multiple parts M2000](#)  
[Basic Molding Kit for smaller parts M2010](#)

**It's Easy!**  
Order all your  
supplies for this  
project on-line  
at Tech Support:  
**661.823.0108**  
Mon - Fri  
7:30am-4pm PST